

GUANGZHOU CITY DALANG SEAT CO., LTD
 NO.1, EAST LONGHE ROAD, YONGXING, TAIHE TOWN, BAIYUN DISTRICT, GUANGZHOU

The following sample(s) was / were submitted and identified on behalf of the client as:

Sample Description : PVC ARTIFICIAL LEATHER/FOAM
 SGS Ref. No. : SDFS1907004532FF
 Manufacturer : GUANGZHOU CITY DALANG SEAT CO., LTD
 Sample Receiving Date : Jul.23, 2019
 Test Performing Date : Jul.23, 2019 to Aug.09, 2019

Test Result Summary

Test(s) Requested	Result(s)	Comments
Schedule 4 Part I and Schedule 5 Part I of Furniture and Furnishings (Fire) (Safety) Regulations 1988 With Amendments In 1989, 1993 and 2010 of United Kingdom	PASS	/
Schedule 1 Part I of Furniture and Furnishings (Fire) (Safety) Regulations 1988 With Amendments In 1989, 1993 and 2010 of United Kingdom	PASS	/
For further details, please refer to the following page(s)		

Signed for and on behalf of
 Shunde Branch
 SGS-CSTC Co., Ltd.




Heather Meng
 Approved signatory



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC Inspection & Testing Services Co., Ltd.
 Shunde Branch Harbin

1/F, 1st Building, European Industrial Park, No.1 Shunde South Road, Wusha Section, Daliang Town, Shunde, Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn
 中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 e sgs.china@sgs.com

Test 1

Test Conducted:

The Test, Specified in Schedule 4 Part I and Schedule 5 Part I of the Furniture and Furnishings (Fire) (Safety) Regulations, is based on BS 5852: Part 1: 1979.

To assess the ignitability of visible cover used in upholstered components when subjected to ignition source 0 and 1.

General Information:

Materials	Leatherette	Weight	Approximately 758 g/m ²
Soaking Condition:	<input checked="" type="checkbox"/> YES (BS5651,specified in UK Regulations)		
Precondition	Indoor Ambient Condition		72 h
Conditioning of Test Specimen and Ignition Source(s)	Temperature: (23±2) °C;Relative Humidity: (50±5) % Duration:24 h;		
Testing Enclosure (fume cupboard / room)	29.3 °C	RH 67 %	---

Test Results:

The following test results relate only to the ignitability of the combination of materials under the particular condition of test. They are not intended as a means of assessing the full potential fire hazard of the materials or products in use.

(A) Smoldering Cigarette Test (ignition source 0)

Criteria	1 st test	2 nd test
9.2.3) Whether the evidence of progressive smoldering or flaming is observed in the interior and/or cover	NO	NO
9.2.4) Whether progressive smoldering or flaming of the sample is observed at any time within one hour of placement of the cigarette	NO	NO
9.2.5) Whether progressive smoldering is observed on final examination when dismantle assembly and examine internally	NO	NO

Test Details:

The filling material for Schedule 4 Part I was non-fire retardant polyurethane foam corresponding to the specification set out in BS 3379 Type B Hardness grade 130 and of a density of 20-22 kg per m³.

Test	Ignition Source	Time to extinction after placement of the cigarette			Rating, comments and observation
		Progressive Smoldering Time(second)	Flame Ceased Time(second)	Smoking Ceased Time	
1 st	0	0	0	04min12s	#1
2 nd	0	0	0	03min38s	#1

Sub-Conclusion: PASS



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

(B) Butane Flame Test (ignition source 1)

Criteria	1 st test	2 nd test
9.3.4) Whether the evidence of flaming or progressive smouldering in the interior and/or cover is observed beyond 120s of the removal of the burner tube	NO	NO
9.4) Whether progressive smoldering is observed on final examination when dismantle assembly and examine internally	NO	NO

Test Details:

The filling material for Schedule 5 Part I was non-fire retardant polyurethane foam corresponding to the specification set out in BS 3379 Type B Hardness grade 130 and of a density of 20-22 kg per m³.

Test	Ignition Source	Ignition Time	Time to Extinction after Removal of the Burner(second)		Rating, comments and observation
			Flame Ceased Time	Smoking Ceased Time	
1 st	1	(20±1)s	0	9	#3
2 nd	1	(20±1)s	0	10	#3

Sub-Conclusion: PASS

Remark: N/A--Not Applicable; N/C--Not Conduct;

- #1—Pass, cigarette fails to smoulder its complete length;
- #2—Pass, cigarette passes to smoulder its complete length, but the sample was not ignition;
- #3—Pass, the sample was not ignited after removal of the burner;
- #4—Pass, flaming but self-extinguishment;
- #5—Fail, extinguished by operator, escalating flaming combustion;
- #6—The first test failed, so retest was not conducted.

Photo Appendix:



Test 2

Test Conducted:

The Test, Specified in Schedule 1 Part I of the Furniture and Furnishings (Fire) (Safety) Regulations, is based on BS 5852: Part 2: 1982.

To assess the ignitability of polyurethane foam in slab used in upholstered components when subjected to ignition source 5.

General Information:

Materials	Foam	Density	Approximately 88.4 kg/m ³
Specified Thickness of Specimen	(75±2) mm	Actual Thickness of Specimen	76 mm

Precondition	Indoor Ambient Condition		72 h
Conditioning of Test Specimen and Ignition Source(s)	Temperature: (23±2) °C; Relative Humidity: (50±5) % Duration: 24 h;		
Testing Enclosure (fume cupboard / room)	29.3 °C	RH 67 %	---

Test Results:

The following test results relate only to the ignitability of the combination of materials under the particular condition of test. They are not intended as a means of assessing the full potential fire hazard of the materials or products in use.

Test Criteria	Results	
	1 st test	2 nd test
(A) Progressive smouldering (Clause 4.1 of BS 5852: Part 2: 1982)		
4.1 b) Any composite that product externally detectable amounts of smoke, heat or glow 60 min after ignition of the crib.	NO	NO
4.1 c) Any composite that displays escalating combustion behaviour so that it is unsafe to continue the test and requires forcible extinction.	NO	NO
4.1 d) Any composite that smoulders until it is essentially consumed within the test duration relevant to the source	NO	NO
4.1 e) Any composite that smoulders to the extremities of the specimen viz upper or lower margins, either side or to its full thickness, within the duration of the test.	NO	NO
4.1 f) Any composite that, on the final examination, shows evidence of charring other than discolouration, more than 100 mm in any direction apart from upwards from the nearest part of the original position of the source.	NO	NO



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

Test Criteria	Results	
	1 st test	2 nd test
(B) Flaming (Clause 4.2 of BS 5852: Part 2 :1982)		
4.2 b) Any composite that continues to flame for more than 10 minutes after the ignition of the crib.	NO	NO
4.2 d) Any composite that displays escalating combustion behaviour so that it is unsafe to continue the test and forcible extinction is required.	NO	NO
4.2 e) Any composite that burns until it is essentially consumed within the test duration relevant to the source.	NO	NO
4.2 f) Any composite on which any flame front reaches the lower margin, either side or passes through the full thickness of the specimen within the duration of the test.	NO	NO
(C) Mass Loss (Clause 5 in Schedule 1 Part1 of UK Regulations)		
If failure against the criteria of clause 4 of BS 5852:Part 2 has occurred but only by way of damage exceeding the limits defined in clause 4.1(e), 4.1(f) and 4.2(f) and provided that the resultant mass loss is less than 60g the foam passes the ignitability test.	22 g	31 g

Test Details:

The cover materials for this test were 100 percent flame retardant polyester fibres specified in Schedule 1, Part I of the Regulations.

Test No.		1 st	2 nd
Duration of	Ignition source (min, sec)	02min07s	02min16s
	Flames (min, sec)	03min59s	04min12s
	Smoke (min, sec)	08min24s	08min44s
Extent of damage of horizontal component	Foam - Width (mm)	86	94
	Foam - Length (mm)	115	121
	Foam - Depth (mm)	34	36
Extent of damage of vertical component	Foam - Length (mm)	102	107
	Foam - Depth (mm)	32	38
The initial mass of the sample composite (g)		7243	7274
The final mass of sample composite(g)		7221	7243
The final mass loss of the composite(g)		22	31
Rating, comments & observations		#1	#1

Conclusion: PASS



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

Remark: N/A--Not Applicable; N/C--Not Conduct;


#1—Pass, flaming but self-extinguishment, the resultant mass loss is less than 60g;

#2—Fail, flaming but self-extinguishment, the resultant mass loss is more than 60g;

#3—Fail, extinguished by operator, escalating flaming combustion;

#4—The first test failed, so retest was not conducted;

Photo Appendix:

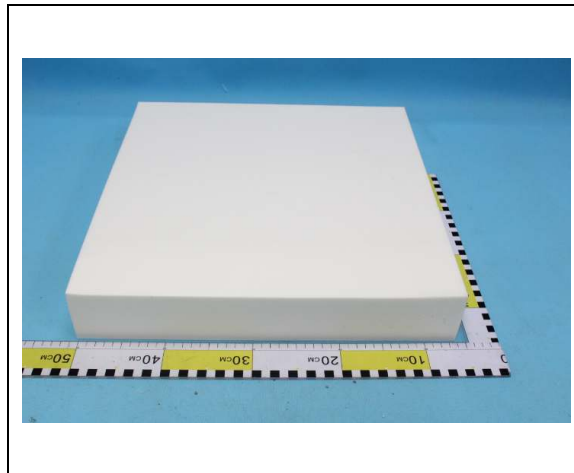

End of Report

